

## Rubbery neat carbon aerogels

Yongsheng Chen\*

Key Laboratory for Functional Polymer Materials and Centre for Nanoscale Science and Technology, Institute of Polymer Chemistry,  
College of Chemistry, Nankai University, Tianjin 300071, China

Received March 23, 2018; accepted March 26, 2018; published online May 24, 2018

**Citation:** Chen Y. Rubbery neat carbon aerogels. *Sci China Chem*, 2018, 61: 971–972, <https://doi.org/10.1007/s11426-018-9251-6>

Polymeric elastomers possess unique elastic mechanical properties that set them apart from other materials, and enable wide applications in a large variety of products such as elastic films, foams and tires. The polymer chains tend to be coil-like due to thermal fluctuation but can also be straightened by external forces, leading to large reversible deformations. But essentially all elastic polymers soften and break down at high temperatures and more typically, undergo glass transition and gradually become hard and brittle and lose the elasticity at lower temperatures. As to inorganic materials, the short-range strong ionic/covalent bonds limit their elastic transformation, which only offers very small reversible elongations. Light-weight, super compressible carbon aerogels with multi-functionalities, such as high conductivity, and light driven response [1] and so on, are providing a promising platform to overcome such limits. Their compress elasticity has been achieved but the stretching elasticity is extremely poor. As a result, to achieve such a carbon-only based rubber with high stretching elasticity still remains a great challenge.

Recently, the group led by Prof. Gao and Xu [2] at Zhejiang University overcome the stretchable brittleness of neat carbon aerogels using graphene as the building block with a hierarchical structure ranging from the nanometer to centimeter scale. The synergy of the hierarchical structure across multi-scales together with pre-buckled micro conformations is an important strategy to enable a macroscopic object or material flexible and stretchable to conform to complicated


deformations, if the proper building block is used. This useful strategy has been found often in the mother nature, such as the growth of embryos to leaves in plants and wrinkles on our skins.

The authors fabricated their hierarchical graphene-carbon nanotube (CNT) aerogels by 3D printing, freeze-drying and confined reduction (Figure 1(a)). This procedure endowed carbon aerogels with tunable hierarchy and high elasticity. The aerogels are able to be reversibly stretched to more than triple their original length (Figure 1(b)) and maintained initial macroscopic shape and microstructures after more than million cycles of stretching and release. In addition, the elasticity could be well maintained from  $-198$ – $500$  °C (Figure 1(c)), surpassing the all traditional polymer elastomers which become viscous or brittle in extreme temperatures.

Guo and colleagues' work [2] also revealed the root of synergistic effect between two types of carbon nanomaterial with mixed topologies. They used a strain-induced buckling metrology [3] to assess the enhancement effect of CNT and proved that the elasticity modulus and fatigue resistance are improved dramatically by introducing CNT.

Furthermore, profiting from the integration of ink-print technique, the deformation behavior of carbon lattices can be programmed to meet various application needs. This new ultralight carbon rubber with tunable stretchability and compressibility can be used as logically strain sensors to decipher motion modes of a “snake” robotic arm. Its good electric conductance may lead to a host of new applications of carbon aerogels as multifunctional components in actua-

\*Corresponding author (email: [yschen99@nankai.edu.cn](mailto:yschen99@nankai.edu.cn))

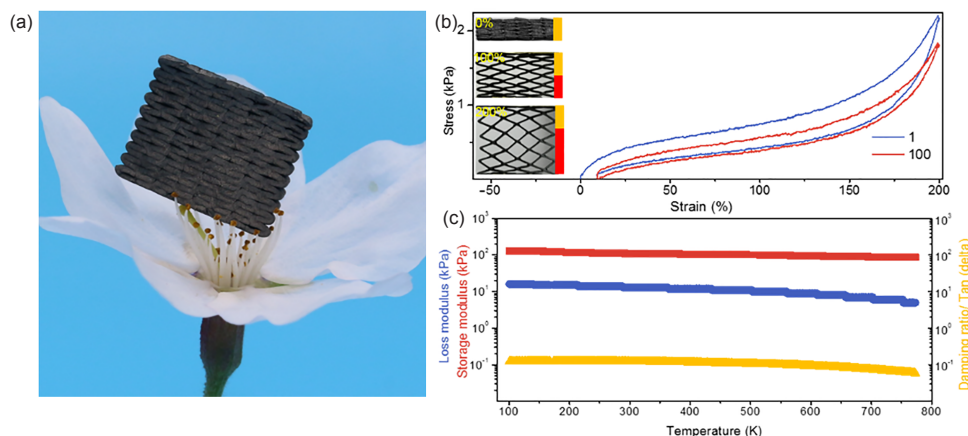

**Figure 1** (a) A digital photograph of ultralight rubbery carbon aerogel with density of  $5.7 \text{ mg/cm}^3$  floating on a flower. (b) Cyclical tensile-release curves for a designed carbon aerogel with stretchable ratio of 200%. (c) Storage modulus (red), loss modulus (blue), and damping ratio (yellow) as function of temperature [2] (color online).

tors, sensors, soft robots and wearable devices. The results indicate that neat carbon materials can possess rubber stretchable elasticity with other advantages such as ultralightness, temperature invariance and mechanically robust performance. This might also offer some hints to design more exciting multifunctional materials using the recently emerged other 2D nanomaterials and even conventional inorganic constituents and ceramics.

**Conflict of interest** The author declares no conflict of interest.

- 1 Zhang T, Chang H, Wu Y, Xiao P, Yi N, Lu Y, Ma Y, Huang Y, Zhao K, Yan XQ, Liu ZB, Tian JG, Chen Y. *Nat Photon*, 2015, 9: 471–476
- 2 Guo F, Jiang Y, Xu Z, Xiao Y, Fang B, Liu Y, Gao W, Zhao P, Wang H, Gao C. *Nat Commun*, 2018, 9: 881
- 3 Stafford CM, Harrison C, Beers KL, Karim A, Amis EJ, VanLandingham MR, Kim HC, Volksen W, Miller RD, Simonyi EE. *Nat Mater*, 2004, 3: 545–550